

Radiological characterization and dose assessment of Israeli concrete

Measurement, dose
assessment and the
impact of concrete aging

Confidential

Under the contract of NCAB

author(s):	G. de With 	reviewed:	R. Kollaard 
name:	17 144718 913155 ReportRnGamma_NCAB- 171012-OldDataSet.docx	approved:	G. Kuipers 
referencnr.:	913155/17.144718		
18 pages	12/10/2017		

© NRG 2016

Subject to agreement with the client, the information contained in this report may not be disclosed to any third party and NRG is not liable for any damage arising out of the use of such information.

Contents

List of tables	4
List of figures	4
Summary	5
Introduction	7
1 Testing and modelling methods	9
1.1 Experimental testing	9
1.1.1 Activity concentrations	9
1.1.2 Radon exhalation rate	9
1.2 Modelling approach	11
1.2.1 Radon and radon progeny	11
1.2.2 Dose modelling	11
2 Results	13
2.1 Experimental results	13
2.1.1 Activity concentrations	13
2.1.2 Radon exhalation rate	13
2.2 Modelling results	14
2.2.1 Indoor radon and radon progeny concentration	14
2.2.2 Dose modelling	16
3 Conclusions	17
4 References	18



List of tables

Table 1 Activity concentrations with its standard uncertainty (± 1 SD) expressed in $\text{Bq}\cdot\text{kg}^{-1}$, and radon exhalation rate with its standard uncertainty (± 1 SD) expressed in $\mu\text{Bq}\cdot\text{s}^{-1}$ and $\mu\text{Bq}\cdot(\text{kg}\cdot\text{s})^{-1}$. 14

Table 2 Radon and radon progeny in $\text{Bq}\cdot\text{m}^{-3}$ and annual dose from radiation exposure in mSv per year. 14

List of figures

Figure 1 Schematic view of the measuring arrangement for determination of the radon exhalation rate according to NEN 5699..... 10

Summary

The aim of this study is to investigate the radiation impact from concrete used in building construction with fly ash compared against concrete without. For this purpose two concrete mixtures are studied to determine the activity concentrations and the radon exhalation, followed by an assessment of the radiation dose when these concrete mixtures are used in regular dwellings. The concrete mixtures include a reference concrete without fly ash, followed by one with fly ash. The radon exhalation is measured twice, once six months after production followed by a measurement 16 months later. Experiments were carried out in compliance with the Dutch standards NEN 5697 and NEN-ISO 11665-9. The results demonstrate a total annual radiation dose from concrete with no fly ash starting at 0.98 mSv reducing to 0.80 mSv after second measurement of the radon exhalation. For concrete with fly ash the annual dose starts at 0.80 and reduces to 0.78 mSv.

Introduction

Fly ash – a by-product of burning pulverized coal in an electrical generating station – is at present widely used as a supplementary cementitious material in the production of cement and concrete. In cement fly ash is found as a partial replacement of clinker, while in concrete it is used as a replacement of sand and cement. Its potential as a supplementary material has been known almost since the start of the last century and offers significant benefits. However, as for all materials of mineral origin fly ash is a source for natural radioactivity, due to the presence of ^{226}Ra (radium), ^{232}Th (thorium) and ^{40}K (potassium). These radionuclides are a source for gamma-emitting (decay) products in the building materials resulting in an external radiation dose to the inhabitant. Furthermore, the presence of ^{226}Ra also provides a source of radon and contributes to the radon exposure.

The aim of this study is to investigate the radiation impact from concrete used in building construction with fly ash additive compared against concrete without. For this purpose two different concrete mixtures are studied, which include one without fly ash followed by a concrete with fly ash. The concrete mixtures are tested in the laboratory to determine its radiological properties, followed by a radiological assessment to determine the radiation exposure from external radiation and radon for a typical room construction.

This report first describes the methods to determine the radiological properties of the concrete mixtures and the modelling techniques used in the assessment. The method description is followed by an overview of the results and ends with a summary of the main findings.

1 Testing and modelling methods

1.1 Experimental testing

As part of the presented work a total of two concrete mixtures (with and without fly ash) are studied to determine the activity concentrations from ^{226}Ra , ^{232}Th (^{228}Ra and ^{228}Th) and ^{40}K , and the radon exhalation rate. For this purpose concrete samples were provided in dual. The activity content was determined in three identical samples ($0.1 \times 0.1 \times 0.1 \text{ m}^3$) for each concrete mixture. These samples were crushed by the laboratory prior to the measurements with a particle size smaller than 0.1 cm. The radon exhalation rate is measured in a single test using a separate set of three identical samples ($0.1 \times 0.1 \times 0.2 \text{ m}^3$).

1.1.1 Activity concentrations

The natural radioactivity concentrations (a in $\text{Bq}\cdot\text{m}^{-3}$) of the specimens are determined according to a standard method published under NEN 5697^[3,4]. According to this method the density dependent photo peak efficiencies are determined for the gamma-ray energies 352 keV (^{214}Pb , parent ^{226}Ra), 583 keV (^{208}Tl , parent ^{228}Th), 911 keV (^{228}Ac , parent ^{228}Ra) and 1,461 keV (^{40}K). Four calibration standards are assembled with increasing densities. The materials used are stearic acid, starch, gypsum and quartz sand, homogeneously mixed with certified amounts of ^{238}U and ^{232}Th , in equilibrium with their daughter nuclides, and ^{40}K . The standards are placed into Marinelli beakers with a volume of about 1 liter, weighted and closed radon-tight. To obtain secular equilibrium, a waiting time of at least three weeks is taken into account before counting the samples. All samples are counted using an HPGe detector in a low-background facility. The samples of the material are analysed in an identical way as the calibration standards with respect to geometry, waiting time and radon-tightness of the beaker. The photo-peak efficiencies of the samples are deduced from the efficiency curves of the standard samples by interpolation. The results are expressed per unit of dry weight.

1.1.2 Radon exhalation rate

The natural free radon exhalation rate (ER_{Rn} in $\text{Bq}\cdot(\text{kg}\cdot\text{s})^{-1}$) of the concrete samples is determined according to the standard method published under NEN 5699^[5]. Determination of the radon exhalation rate is based on a continuous ventilation of an exhalation chamber with material sample. On the outlet

side of the chamber the ^{222}Rn from the material sample is collected and subsequently quantified using liquid scintillation counting. For this purpose an exhalation chamber with an approximate volume of around 36 liter is required. A constant flow of radon-free nitrogen gas of known humidity is passed through the chamber. The relative humidity of the nitrogen flow is regulated within the full range of 0 to 100% by means of a controlled mixing of dry and water-saturated nitrogen gas (Figure 1). After a given time (normally within 3 h) a steady-state concentration is reached and the experiment can be started. The out coming flow is guided through two U-shaped tubes for a period of 10 to 30 minutes. The first tube contains KOH tablets to dry the gas flow; the second tube contains 4 g of silica gel and is cooled with liquid nitrogen to trap the radon. After absorption, the tube with silica gel is warmed and subsequently the content is poured into a counting vial containing toluene-based scintillation liquid. During this process no loss of ^{222}Rn was observed.

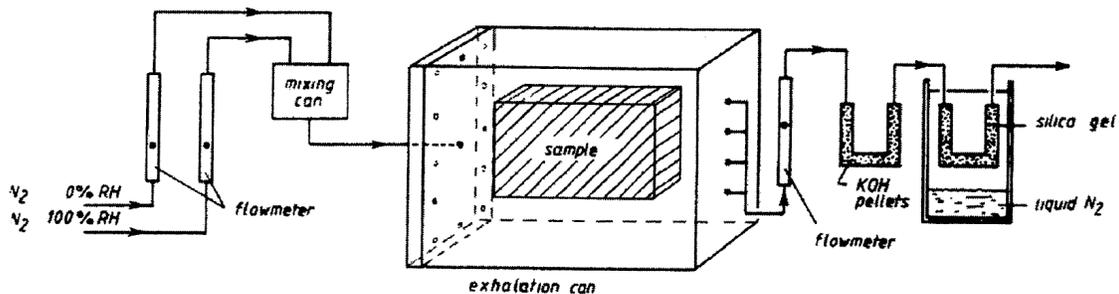


Figure 1 Schematic view of the measuring arrangement for determination of the radon exhalation rate according to NEN 5699.

Radioactive equilibrium in the counting vial is attained after around 3 h, and a further 13 h is required before the radon progeny in the vial is in equilibrium. Subsequently, a recording of the spectrum is performed using a liquid scintillation spectrometer. For an optimal count rate the window settings are set from 110 to 600 keV. Under these conditions a counting efficiency of approximately $2.8 \text{ c}\cdot\text{s}^{-1}\cdot\text{Bq}^{-1}$ can be reached.

The samples are conditioned at a temperature of $20 \pm 2^\circ\text{C}$ and a relative humidity of $50 \pm 5\%$. Equilibrium is achieved when the mass of the sample over a period of seven days deviates by less than 0.07% from the value determined during the previous measurement. For fresh concrete a minimum curing period of at least 28 days is required.

1.2 Modelling approach

1.2.1 Radon and radon progeny

In this work a Computational Fluid Dynamics (CFD) model is used to simulate the concentration of radon and radon progeny concentrations (C) in a standard Israeli shelter room (which is made of massive concrete). The dispersion of air and radon (progeny) is computed using the fundamental flow equations for gas and aerosols, which enables detailed simulation of the three-dimensional flow structures from ventilation and buoyancy. Algorithms are incorporated and coupled with the CFD model to take account of all relevant physical processes. These include the formation and attachment of the progeny products to aerosol particles as well as the dispersion and deposition of the radioactive aerosols. Further details on the modelling technique are described by De With and De Jong^[6]. The computations are performed using the radon exhalation rate (ER_{Rn}) as measured according to NEN 5699 and applied to all wall surfaces.

1.2.2 Dose modelling

External dose

The external exposure component of the effective dose (E_{Ex}) from the building materials in the room is calculated according to the method described by De Jong and Van Dijk^[7,8]. The method is based on a standard room geometry of 5 by 4 m and 2.8 m in height as defined by Koblinger^[9]. Each construction part (i.e. floor, walls and ceiling) is made of 20 cm thick concrete and no doors or windows. Correction factors are deduced for alternative situations. The absorbed dose rate in air (unit: $Gy \cdot h^{-1}$) in a particular room is then calculated according to:

$$\dot{D}_{air} = \left\{ \sum_{i=1}^6 [F_{dose} \cdot F_1 \cdot F_2 \cdot F_3 \cdot \dots \cdot F_n]_i \right\} F_{zoning} \cdot F_{adjac} \quad (1)$$

in which i is the index for a construction part, F_1 to F_n are correction factors for each construction part i , where $n=4$. F_{zoning} is a correction factor which takes internal zoning of the construction into account, and F_{adjac} is the contribution from adjacent floors and dwellings. F_{dose} is the so-called dose factor, defined as: $F_{dose,i} = k_1 \cdot a_{1,i} + k_2 \cdot a_{2,i} + k_3 \cdot a_{3,i}$. In this equation k_1 , k_2 and k_3 represent the specific absorbed dose rates, and $a_{1,i}$, $a_{2,i}$ and $a_{3,i}$ the activity concentrations of ^{226}Ra , ^{232}Th and ^{40}K of construction part i ($\text{Bq} \cdot \text{kg}^{-1}$), respectively. The activity concentrations are obtained experimentally according to NEN 5697. The values of the specific absorbed dose rate depend amongst others on the thickness, density and dimensions of the various construction parts and are selected as 0.90, 1.10 and 0.08 $\text{nGy} \cdot \text{h}^{-1}$ per $\text{Bq} \cdot \text{kg}^{-1}$ respectively^[10]. The absorbed dose is multiplied with a conversion factor of 0.7 $\text{Sv} \cdot \text{Gy}^{-1}$ to obtain the effective dose E_{Ex} .



Radon dose

The radon component of the effective dose (E_{Rn}) in mSv per year is computed according to UNSCEAR^[11]:

$$E_{Rn} = DCC_{Rn} \cdot EEC_{Rn} \cdot t_{Rn}, \quad (2)$$

where DCC_{Rn} is the dose conversion coefficient of $9 \text{ nSv}\cdot\text{h}^{-1}$ per $\text{Bq}\cdot\text{m}^{-3}$, EEC_{Rn} the equilibrium equivalent ^{222}Rn concentration and t_{Rn} is the hours per year spent indoors. The EEC_{Rn} is calculated as $EEC_{Rn} = 0.105C_1 + 0.515C_2 + 0.380C_3$, where C_1 , C_2 and C_3 are the activity concentrations in the indoor environment of ^{218}Po , ^{214}Pb and ^{214}Bi ($\text{Bq}\cdot\text{m}^{-3}$), respectively. These concentrations are obtained from the CFD computations.

2 Results

2.1 Experimental results

2.1.1 Activity concentrations

A gamma-spectrometric analysis on the radioactivity concentrations of the gamma-ray emitting radionuclides is carried out in three samples of each of the two concrete mixtures. The results from these measurements are presented in Table 1. The results demonstrate a ^{226}Ra ranging between 29 and 39 $\text{Bq}\cdot\text{kg}^{-1}$ with elevated ^{226}Ra concentrations for the mixture with fly ash (B series). The concentrations ^{228}Ra and ^{228}Th , which are both part of the ^{232}Th series are in the order of 8 to 18 $\text{Bq}\cdot\text{kg}^{-1}$. In each mixture the nuclide concentration of ^{228}Ra and ^{228}Th is broadly similar indicating that the thorium decay series is in secular equilibrium. The concentrations for ^{40}K range between 50 to 65 $\text{Bq}\cdot\text{kg}^{-1}$ and also here the activity in the mixtures with fly ash is higher.

2.1.2 Radon exhalation rate

To obtain the ^{222}Rn exhalation rate a single test is carried out twice for each concrete mixture according to the Dutch standard NEN 5699^[5]. The results from these experiments are presented in Table 1 and show a radon exhalation rate (ER_{Rn}) of 5.4 and 10.5 $\mu\text{Bq}\cdot(\text{kg}\cdot\text{s})^{-1}$ six months after production, for the mixture with and without fly ash, respectively. The exhalation rates drops to respectively 4.8 and 6.8 $\mu\text{Bq}\cdot(\text{kg}\cdot\text{s})^{-1}$, showing a considerable drop in exhalation particular for the concrete without fly ash. The radon exhalation from the mixtures with fly ash is in most cases lower. Table 1 also shows the radon exhalation factor (ER_f), which is defined as the ratio between the amount of radon released to the environment and the amount that is generated within the material, and represents the percentage of radon that is released from the material. The factor is computed as $ER_f = ER_{Rn} / (C_{Ra-226} \cdot \lambda_{Rn})$, where ER_{Rn} is the exhalation rate in $\text{Bq}\cdot(\text{kg}\cdot\text{s})^{-1}$, C_{Ra-226} the radium concentration in $\text{Bq}\cdot\text{kg}^{-1}$ and λ_{Rn} the radon decay constant. The ER_f is lower for the mixture with fly ash and demonstrates that the percentage of radon released is reduced when fly ash is added.

Table 1 Activity concentrations (a) with its standard uncertainty (± 1 SD) expressed in $\text{Bq}\cdot\text{kg}^{-1}$, and radon exhalation rate (ER) with its standard uncertainty (± 1 SD) expressed in $\mu\text{Bq}\cdot\text{s}^{-1}$ and $\mu\text{Bq}\cdot(\text{kg}\cdot\text{s})^{-1}$.

Survey 2013	Activity concentrations				Radon exhalation		
	$a_{\text{Ra-226}}$	$a_{\text{Ra-228}}$	$a_{\text{Th-228}}$	$a_{\text{K-40}}$	ER_{Rn}	ER_f	
Sample	($\text{Bq}\cdot\text{kg}^{-1}$)	($\text{Bq}\cdot\text{kg}^{-1}$)	($\text{Bq}\cdot\text{kg}^{-1}$)	($\text{Bq}\cdot\text{kg}^{-1}$)	($\mu\text{Bq}\cdot\text{s}^{-1}$)	($\mu\text{Bq}\cdot(\text{kg}\cdot\text{s})^{-1}$)	(%)
AQ-1	29.5±0.2	8.7±0.2	9.2±0.2	60.2±1.0			
AQ-2	29.6±0.2	9.6±0.3	9.0±0.2	57.1±0.9			
AQ-3	29.2±0.2	7.7±0.2	7.6±0.2	50.9±0.8			
AQ	29.4±0.2	8.7±0.2	8.6±0.2	56.1±0.9			
AP 4-6	Measured: September 2010				149.0±3.3	10.5±0.2	17.0
	Measured: January 2012				96.6±3.2	6.8±0.2	11.0
BQ-7	38.3±0.3	18.6±0.4	17.8±0.3	64.8±1.0			
BQ-8	38.9±0.3	17.6±0.3	18.6±0.3	57.1±0.9			
BQ-9	36.6±0.3	18.1±0.3	18.0±0.3	60.7±1.0			
BQ	37.9±0.3	18.1±0.3	18.1±0.3	60.9±1.0			
BP 10-12	Measured: September 2010				74.0±6.2	5.4±0.5	6.8
	Measured: January 2012				65.2±2.5	4.8±0.2	6.0

2.2 Modelling results

Based on the experimental findings reported in Section 2.1 the dose from external radiation and radon is computed using the methods described in Section 1.2. For the computation a room with 20 cm thick concrete walls, floor and ceiling is assumed. The time spent indoors is taken as 7000 h per year, which corresponds with 80% of the total time^[11].

2.2.1 Indoor radon and radon progeny concentration

CFD calculations are performed for the four concrete mixtures according to Section 1.2.1. The modelling is based on a ventilated room with an air exchange rate of 0.5 h^{-1} . The radon exhalation applied at the wall is obtained from the experimental data presented in Table 1. For this purpose the measured radon exhalation is corrected with a correction factor of 0.79^[12]. This correction is required as the radon exhalation is measured from all six surfaces of the sample, while under real conditions the exhalation is one-dimensional and will only take place from the two outer surfaces of the building element. The

background concentration is $10 \text{ Bq}\cdot\text{m}^{-3}$ with an equilibrium factor between radon and its progeny of 0.4^[11]. Further model assumptions are as follows;

Room dimensions	: length 3 m; width 3 m; height 2.7 m
Inner area (A_{Ro})	: 50.4 m^2
Volume (V)	: 24.3 m^3
Window (A_{Wi})	: $1.2 \times 1.2 \text{ m}^2$ (1.4 m^2)
Door (A_{Do})	: $2.0 \times 0.8 \text{ m}^2$ (1.6 m^2)
Area concrete (A_{Co})	: 47.4 m^2
Concrete thickness (L)	: 0.2 m
Concrete density (ρ)	: $2300 \text{ kg}\cdot\text{m}^{-3}$
Furniture	: Unfurnished room

The computed concentrations for radon and its progeny (C) are presented in Table 2. The radon concentrations are in the order of 20 to $40 \text{ Bq}\cdot\text{m}^{-3}$, and the progeny concentrations are reduced to around $5 \text{ Bq}\cdot\text{m}^{-3}$ for ^{214}Bi due to natural ventilation and deposition of the radon progeny. The concentrations include the radon background of $10 \text{ Bq}\cdot\text{m}^{-3}$ and its background progeny.

Table 2 Radon and radon progeny (C) in $\text{Bq}\cdot\text{m}^{-3}$ and annual dose from radiation exposure (E) in mSv per year, with its standard uncertainty (± 1 SD), where $E_{Tot}=E_{Ex}+E_{Rn}$. The reported uncertainty is based on the experimental uncertainty reported in Table 1.

Survey 2013	Radon (progeny)				Annual effective dose		
	C_{Rn-222} ($\text{Bq}\cdot\text{m}^{-3}$)	C_{Po-218} ($\text{Bq}\cdot\text{m}^{-3}$)	C_{Pb-214} ($\text{Bq}\cdot\text{m}^{-3}$)	C_{Bi-214} ($\text{Bq}\cdot\text{m}^{-3}$)	E_{Ex} ($\text{mSv}\cdot\text{yr}^{-1}$)	E_{Rn} ($\text{mSv}\cdot\text{yr}^{-1}$)	E_{Tot} ($\text{mSv}\cdot\text{yr}^{-1}$)
AQ 2010	36.9±0.6	31.2±0.5	13.0±0.2	6.6±0.1	0.20±0.001	0.79±0.01	0.98±0.01
AQ 2012	27.4±0.6	23.3±0.5	9.9±0.2	5.1±0.1	0.20±0.001	0.60±0.01	0.80±0.01
BQ 2010	23.9±1.2	20.4±1.0	8.8±0.4	4.6±0.2	0.29±0.002	0.53±0.02	0.82±0.02
BQ 2012	22.3±0.5	19.0±0.4	8.2±0.2	4.3±0.1	0.29±0.002	0.50±0.01	0.78±0.01

2.2.2 Dose modelling

External dose

Following the above described results, a dose assessment for external radiation and radon exposure is performed for the sixteen concrete mixtures. For this purpose the concentrations ^{228}Ra and ^{228}Th (a) reported in Table 1 are averaged to obtain an estimated ^{232}Th concentration in the building material. The annual effective dose (E_{Ex}) from the building materials and the background radon is shown in Table 2. The results show a dose from external radiation of around 0.20 to 0.29 mSv per year. The external radiation dose is higher for the sample with fly ash due to its increase in activity concentrations.

Radon dose

The annual effective dose from radon (E_{Rn}) is also shown in Table 2 and is around 0.5 to 0.8 mSv. This includes exposure to radon's background concentration of $10 \text{ Bq}\cdot\text{m}^{-3}$. As a result the dose from radon is considerable higher than the dose from external radiation. By accumulating both doses the total annual dose from external radiation and radon is around 0.8 mSv with a maximum of 0.98 mSv for concrete without fly ash during its first year.

3 Conclusions

A total of two concrete mixtures have been studied to determine the activity concentrations and the radon exhalation, followed by an assessment of the radiation dose when these concrete mixtures are used in regular dwellings. The concrete mixtures include a reference concrete without fly ash, followed by a mixture with fly ash. Experiments were carried out in compliance with the Dutch standards NEN 5697 and NEN-ISO 11665-9.

The results demonstrate a reduction in the total annual radiation dose in the concrete with fly ash. The reduction is most substantial in the first year when the annual dose for both types of concrete is 0.98 mSv without fly ash and 0.82 mSv with fly ash. In the second year the annual dose drops to respectively 0.80 and 0.78 mSv. The reduction is a result of a reduced radon exhalation from the concrete. The total annual dose of the concrete with fly ash is lower due to its lower radon exhalation and despite its higher external radiation.

4 References

- [1] EC (2013)
Council directive 2013/59/EURATOM of 5 December 2013 laying down basic safety standards for protection against the dangers arising from exposure to ionizing radiation, *Off. J. Eur. Union*, L 13/1.
- [2] IAEA (2015)
Protection of the Public against Exposure Indoors due to Radon and Other Natural Sources of Radiation, IAEA Specific Safety Guide No. 32.
- [3] NEN (2001)
Radioactivity measurements – Determination of the natural radioactivity in stony building materials by means of semiconductor gamma ray spectrometry, NEN 5697(en). Nederlands Normalisatie-instituut, Delft, the Netherlands.
- [4] Blaauw, M., Glass, H.J., De Jong, P., and Van Dijk, W. (2001)
The Dutch norm for the determination of natural radioactivity levels in construction materials applied to concrete samples, *J. Radioanal. Nucl. Chem.*, 249, pp. 177-180.
- [5] NEN (2001)
Radioactivity measurements – Determination method of the rate of the radon exhalation of dense building materials, NEN 5699(en). Nederlands Normalisatie-instituut, Delft, the Netherlands.
- [6] De With, G., and De Jong, P. (2016)
Impact from indoor air mixing on the thoron progeny concentration and attachment fraction, *J. Environ. Radio.*, 158-159, pp. 56-63.
- [7] De Jong, P., and Van Dijk, W. (2008)
Modeling gamma radiation in dwellings due to building materials, *Health Phys.*, 94, pp. 33-42.
- [8] De Jong, P., and Van Dijk, J.W.E. (2008)
Calculation of the indoor gamma dose rate distribution due to building materials in the Netherlands, *Radiat. Prot. Dosim.*, 132, pp. 381-389.
- [9] Koblinger, L. (1978)
Calculation of exposure rates from gamma sources in walls of dwelling rooms, *Health Phys.*, 34, pp. 459-463.
- [10] De Jong, P. (2010)
PhD Thesis Exposure to natural radioactivity in the Netherlands: the impact of building materials, Arnhem, The Netherlands.
- [11] UNSCEAR (2006)
Sources and effects of ionizing radiation. UNSCEAR 2000 report to the General Assembly, with scientific annexes. Volume 1: Sources, United Nations Scientific Committee on the Effects of Atomic Radiations. United Nations, New York.
- [12] Berkvens, P., Kerkhove, E., and Vanmarcke H. (1988)
Three-dimensional treatment of steady-state ²²²Rn diffusion in building materials: introducing a practical modified one-dimensional approach, *Health Phys.*, 55, pp. 793-799.